



This is a repository copy of *A Vesicle-to-Worm Transition Provides a New High-Temperature Oil Thickening Mechanism*.

White Rose Research Online URL for this paper:
<http://eprints.whiterose.ac.uk/110625/>

Version: Accepted Version

Article:

Derry, M.J. orcid.org/0000-0001-5010-6725, Mykhaylyk, O.O. and Armes, S.P. orcid.org/0000-0002-8289-6351 (2017) A Vesicle-to-Worm Transition Provides a New High-Temperature Oil Thickening Mechanism. *Angewandte Chemie International Edition*. ISSN 1433-7851

<https://doi.org/10.1002/anie.201609365>

Reuse

Unless indicated otherwise, fulltext items are protected by copyright with all rights reserved. The copyright exception in section 29 of the Copyright, Designs and Patents Act 1988 allows the making of a single copy solely for the purpose of non-commercial research or private study within the limits of fair dealing. The publisher or other rights-holder may allow further reproduction and re-use of this version - refer to the White Rose Research Online record for this item. Where records identify the publisher as the copyright holder, users can verify any specific terms of use on the publisher's website.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

A Vesicle-to-Worm Transition Provides a New High-Temperature Oil Thickening Mechanism

Matthew J. Derry,* Oleksandr O. Mykhaylyk, and Steven P. Armes*

Abstract: Poly(stearyl methacrylate)-poly(benzyl methacrylate) diblock copolymer vesicles are prepared via reversible addition-fragmentation chain transfer (RAFT) dispersion polymerization directly in mineral oil. Such vesicles undergo a vesicle-to-worm transition on heating to 150 °C, as judged by transmission electron microscopy (TEM) and small-angle X-ray scattering (SAXS). Variable temperature ¹H NMR spectroscopy indicates that this transition is the result of surface plasticization of the core-forming block by hot solvent, effectively increasing the volume fraction of the stabilizer block and so reduces the packing parameter for the block copolymer chains. The rheological behavior of a 10% w/w copolymer dispersion in mineral oil is strongly temperature-dependent: the storage modulus increases by five orders of magnitude on heating above the critical gelation temperature of 135 °C, as the non-interacting vesicles are converted into weakly interacting worms. SAXS studies indicate that each vesicle produces on average three worms. Such vesicle-to-worm transitions offer an interesting new mechanism for the high-temperature thickening of oils.

Small molecule amphiphiles such as surfactants are well-known to self-assemble in aqueous solution to form spherical micelles,^[1] lamellae or vesicles (liposomes).^[2] In 1976, Israelachvili and co-workers introduced the concept of a geometric packing parameter for surfactants,^[3] thus allowing their morphology to be predicted based on the relative dimensions of the hydrophilic and hydrophobic components. In 1995, Eisenberg and co-workers^[4] reported the first examples of block copolymer vesicles using highly asymmetric polystyrene-poly(acrylic acid) diblock copolymers. Self-assembly occurred on addition of water, a non-solvent for polystyrene, to a dilute copolymer solution in DMF. Bates and co-workers reported the formation of well-defined block copolymer worms in aqueous solution using poly(ethylene oxide)-polybutadiene diblock copolymers.^[5] Antonietti and Förster subsequently extended the packing parameter concept to include block copolymer spheres, cylinders and vesicles.^[6] More recently, polymerization-induced self-assembly (PISA) has provided a versatile and convenient route for the synthesis of block copolymer spheres, worms or vesicles at relatively high copolymer concentrations in either aqueous,^[7] alcoholic^[8] or non-polar^[9] media. Typically, RAFT dispersion polymerization is utilized to chain-extend a soluble macromolecular chain transfer agent (macro-CTA) with a miscible monomer to form an insoluble polymer block, which drives *in situ* self-assembly. TEM studies have shed new light on the nature of the worm-to-vesicle transition that can occur under

these conditions, which proceeds via a 'jellyfish' intermediate.^[10] PISA formulations have enabled the *rational* synthesis of low-polydispersity vesicles using a binary mixture of two macro-CTAs^[11] and the precise mechanism of vesicle growth during such syntheses has been recently elucidated.^[10a, 12]


PISA enables the convenient preparation of thermoresponsive diblock copolymer nano-objects. For example, a worm-to-sphere transition occurs on *cooling* poly(glycerol monomethacrylate)-poly(2-hydroxypropyl methacrylate) (PGMA-PHPMA) diblock copolymer nanoparticles, because the core-forming PHPMA block becomes more hydrated at lower temperatures.^[13] In contrast, worm-to-sphere transitions are observed on *heating* certain alcoholic and non-polar PISA formulations. In both cases, the ingress of solvent into the cores increases the effective volume fraction of the stabilizer block and hence triggers the morphological transition. Such worm-to-sphere transitions lead to degelation, because the multiple inter-particle contacts formed by the anisotropic worms cannot be maintained by the isotropic spherical nanoparticles.^[13-14]

In the present study, we report a thermally-triggered vesicle-to-worm transition for a PISA formulation in a non-polar solvent (mineral oil). SAXS, rheology and ¹H NMR studies confirm that this order-order transition occurs at elevated temperature, which suggests a unique oil-thickening mechanism.

A low-polydispersity poly(stearyl methacrylate) (PSMA; mean degree of polymerization = 13) macro-CTA was chain-extended via RAFT dispersion polymerization of benzyl methacrylate (BzMA) monomer in mineral oil to generate well-defined PSMA₁₃-PBzMA₉₆ diblock copolymer vesicles at 10% w/w solids (Scheme 1). A BzMA conversion of 96% was obtained for this PISA formulation within 5 h at 90 °C, as judged by ¹H NMR spectroscopy. THF GPC analysis confirmed that the resulting PSMA₁₃-PBzMA₉₆ diblock copolymer chains exhibited a relatively narrow molecular weight distribution ($M_w/M_n = 1.17$). Moreover, the clear shift in the molecular weight distribution curve relative to that of the PSMA₁₃ macro-CTA indicated a high blocking efficiency (see Figure S1). Transmission electron microscopy (TEM) images indicate a well-defined vesicular morphology, see Figure 1a. Small-angle X-ray scattering (SAXS) studies conducted on the 5.0% w/w dispersion of PSMA₁₃-PBzMA₉₆ nanoparticles at 20 °C (red data, Figure 2) indicated a gradient of approximately -2 at low q , as expected for vesicles, with characteristic local minima corresponding to the outer vesicle dimensions ($q \sim 0.05 \text{ nm}^{-1}$) and the vesicle membrane thickness, T_m ($q \sim 0.5 \text{ nm}^{-1}$).

[*] Dr. Matthew J. Derry, Dr. Oleksandr O. Mykhaylyk, Prof. Steven P. Armes
Department of Chemistry
University of Sheffield
Brook Hill
E-mail: m.derry@sheffield.ac.uk; s.p.arnes@sheffield.ac.uk

Supporting information for this article is given via a link at the end of the document.

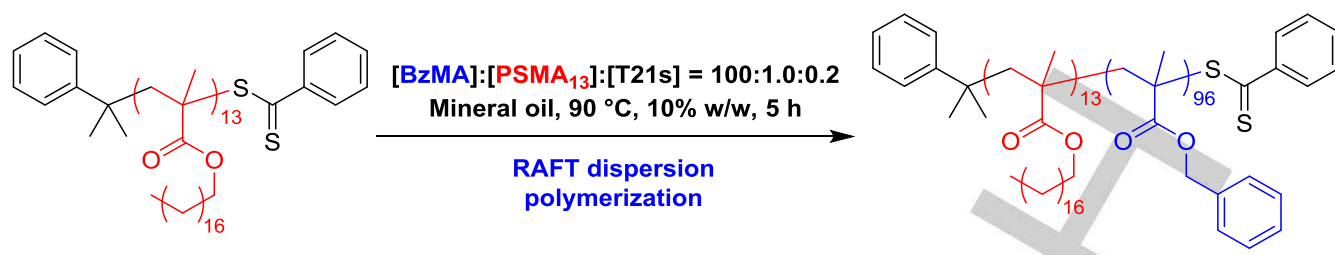

Scheme 1. Synthesis of poly(stearyl methacrylate)₁₃-poly(benzyl methacrylate)₉₆ (PSMA₁₃-PBzMA₉₆) vesicles via RAFT dispersion polymerization of benzyl methacrylate at 10% w/w solids in mineral oil at 90 °C.


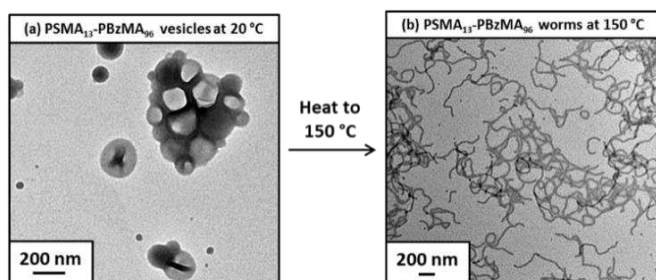


Figure 1. Transmission electron micrographs obtained for (a) 0.1% w/w PSMA₁₃-PBzMA₉₆ vesicles at 20 °C and (b) the highly anisotropic worms formed by the same vesicle dispersion on heating up to 150 °C. methacrylate at 10% w/w solids in mineral oil at 90 °C.

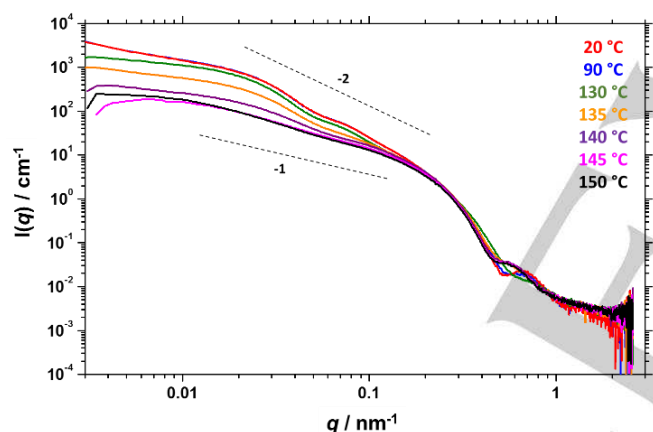

Fielding et al. reported that poly(lauryl methacrylate)-poly(benzyl methacrylate) (PLMA-PBzMA) worms prepared in *n*-dodecane undergo a worm-to-sphere transition upon heating as a result of *surface plasticization* of the PBzMA core-forming

block.^[14b, 14c] Similarly, the PSMA₁₃-PBzMA₉₆ vesicles described in this study exhibited a vesicle-to-worm morphological transition on heating up to 150 °C. In order to observe this change in nanoparticle morphology by TEM, a 10% w/w dispersion of PSMA₁₃-PBzMA₉₆ vesicles was equilibrated at 150 °C for 10 min and diluted with *n*-dodecane at the same temperature to produce a 0.1% w/w dispersion. This hot dilution protocol ensured that the worms were retained as a kinetically-trapped morphology on cooling to 20 °C (see Figure 1b). The temperature-dependence of the vesicle-to-worm transition was then studied in detail using SAXS (Figure 2).

Representative SAXS patterns for 5.0% w/w PSMA₁₃-PBzMA₉₆ nanoparticles in mineral oil (Figure 2) recorded at 20 °C (red data), 90 °C (blue data) and 130 °C (green data) are very similar, indicating that the vesicular morphology is retained throughout this temperature range. Notably, the local minimum at high *q* (~0.5 nm⁻¹) gradually shifts to higher *q*, suggesting that the vesicle membrane thickness decreases over this temperature range. These observations are consistent with greater solvation of the BzMA residues near the block junction on heating, which reduces the effective volume fraction of this membrane-forming block (hence reducing the mean membrane thickness). On heating to 135 °C, a shallower gradient is observed at low *q* (orange data) and the local minimum at high *q* is shifted to lower *q*. This indicates the onset of the vesicle-to-worm transition. SAXS patterns continued to evolve on further heating, with a pure worm phase eventually being obtained at 145 °C (pink data) and 150 °C (black data). This morphological assignment is based on a gradient of approximately -1 at low *q*, as well as the loss of the feature at *q* ~ 0.05 nm⁻¹ which represents the overall vesicle diameter.

Figure 3. Representative SAXS patterns and fittings for PSMA₁₃-PBzMA₉₆ vesicles at 20 °C (top, red data set plus black data fit) and PSMA₁₃-PBzMA₉₆ worms at 150 °C (bottom, black data set plus red data fit). Inset cartoons indicate the mean overall vesicle diameter (*D_v*), vesicle membrane thickness (*T_m*), worm contour length (*L_w*) and worm thickness (*T_w*). Gradients of -2 and -1 are also shown as a guide.

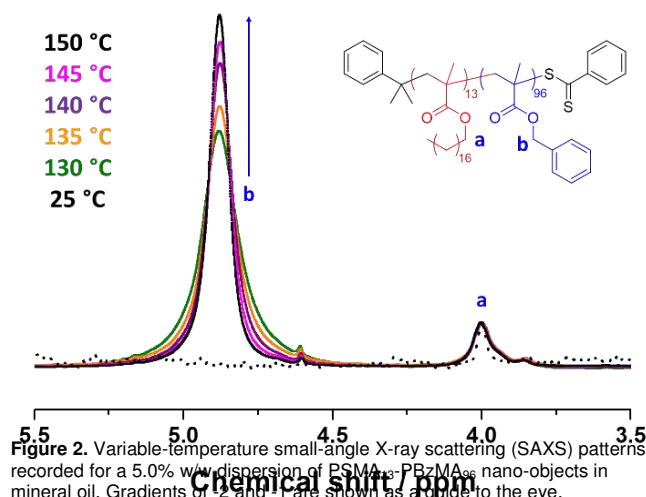


Figure 2. Variable-temperature small-angle X-ray scattering (SAXS) patterns recorded for a 5.0% w/w dispersion of PSMA₁₃-PBzMA₉₆ nano-objects in mineral oil. Gradients of 2 and 1 are shown as a guide to the eye.

Figure 4. Variable-temperature ¹H NMR spectra recorded for 5.0% w/w PSMA₁₃-PBzMA₉₆ nanoparticles in d₂₆-dodecane.

Fitting SAXS patterns acquired at 20 °C and 150 °C using well-known vesicle^[15] and worm-like micelle^[16] models enabled the mean overall vesicle diameter, D_{out} , vesicle membrane thickness, T_m , worm thickness, T_w , and worm contour length, L_w , to be determined (see Figure 3). At 150 °C, the local minimum at $q \sim 0.5 \text{ nm}^{-1}$ indicates that $T_w = 14.5 \text{ nm}$, which is somewhat larger than the T_m observed at 20 °C (8.8 nm). Similar differences were also observed by Rank et al.,^[17] who reported that poly(2-vinyl pyridine)₆₆-poly(ethylene oxide)₄₆ (P2VP₆₆-PEO₄₆) diblock copolymer vesicles formed worms on cooling from 25 °C to 4 °C. These P2VP₆₆-PEO₄₆ vesicles exhibited a T_m of 12 nm at 25 °C compared to a T_w of 16 nm for worms formed from the same diblock copolymer at 4 °C. This was attributed to the interdigitated core-forming blocks producing a more densely packed core within the vesicle membrane - with little or no interdigitation occurring for the corresponding worms.^[17] Geometric calculations based on the PSMA₁₃-PBzMA₉₆ vesicle/worm dimensions determined from SAXS analysis indicate that, on average, each vesicle dissociates to form three worms on heating from 20 °C to 150 °C (see Supporting Information). This observation is in rather good agreement with the ratio of the mean aggregation numbers determined for the vesicles (9784) and worms (3130) calculated from the respective SAXS models (see Supporting Information).

The degree of solvation of the PBzMA core-forming block within the PSMA₁₃-PBzMA₉₆ nano-objects was monitored by variable temperature ¹H NMR spectroscopy. First, the initial PSMA₁₃-PBzMA₉₆ vesicles were transferred from mineral oil into d₂₆-dodecane via three centrifugation-redispersion cycles (see Supporting Information). TEM studies of the final diluted copolymer dispersion in *n*-dodecane confirmed that the vesicles survived this solvent exchange (see Figure S2). ¹H NMR studies of 5.0% w/w PSMA₁₃-PBzMA₉₆ nano-objects in d₂₆-dodecane were conducted from 25 to 150 °C. This aliphatic solvent was selected because it is very similar to the mean chemical composition of mineral oil, which is not commercially available in deuterated form. The benzylic proton signal at ~4.9 ppm became progressively more intense relative to the oxymethylene proton signal of the PSMA block at ~4.0 ppm (see Figure 4), which

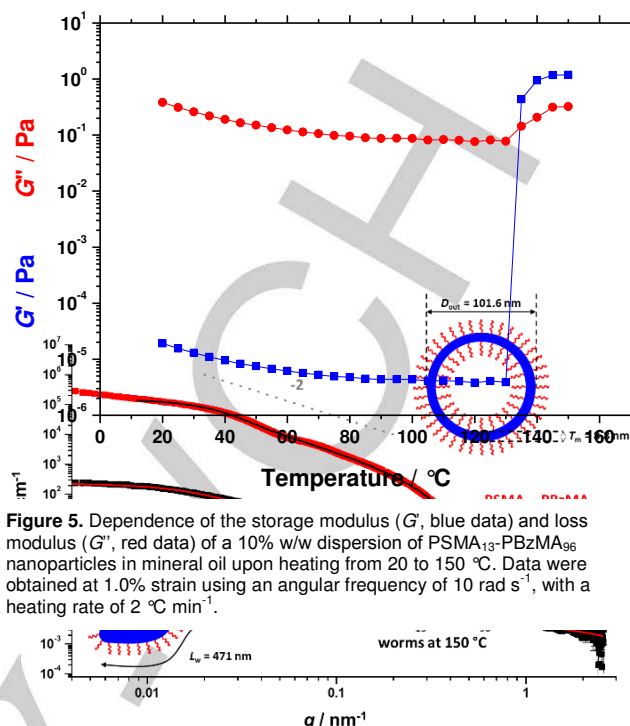


Figure 5. Dependence of the storage modulus (G' , blue data) and loss modulus (G'' , red data) of a 10% w/w dispersion of PSMA₁₃-PBzMA₉₆ nanoparticles in mineral oil upon heating from 20 to 150 °C. Data were obtained at 1.0% strain using an angular frequency of 10 rad s^{-1} , with a heating rate of 2 °C min^{-1} .

indicates greater solvation of the PBzMA block. This indicates solvent ingress into the PBzMA domain at elevated temperatures, causing a change in the preferred diblock copolymer morphology via surface plasticization.^[14b]

It is well-known that (i) dispersions of diblock copolymer worms form free-standing gels at sufficiently high copolymer concentrations,^[5, 18] and (ii) a thermally-triggered worm-to-sphere transition results in rapid in situ degelation.^[13-14] A 10% w/w dispersion of PSMA₁₃-PBzMA₉₆ vesicles in mineral oil was studied to assess the effect of the vesicle-to-worm transition on its rheological behavior (see Figure 5). On heating from 20 °C to 130 °C, the storage (G') and loss (G'') moduli are reduced and G' always remains lower than G'' , which indicates that the dispersion becomes less viscous. Such an inverse relationship between solution viscosity and temperature is well-known for most fluids.^[19] However, on further heating from 130 to 135 °C, G' increases by more than five orders of magnitude up to ~100 Pa. Thus the latter temperature corresponds to the critical gelation temperature (CGT), above which the dispersion behaves as a viscoelastic gel (since G' now exceeds G''). These observations are supported by the SAXS data shown in Figure 2, where PSMA₁₃-PBzMA₉₆ vesicles are observed at temperatures between 20 °C and 130 °C, and the onset of the vesicle-to-worm transition occurred at around 135 °C. The first appearance of anisotropic worm-like particles as judged by SAXS is in close agreement with the CGT determined by rheology, which strongly suggests that multiple inter-worm contacts are responsible for the observed gelation. There are rather few literature examples of significantly higher viscosities being achieved on increasing the solution temperature, with most of these studies involving aqueous formulations.^[13, 20] However, these thermal transitions

typically occur at relatively low temperatures (4 °C to 30 °C) and usually increase the aqueous solution viscosity by less than an order of magnitude. As far as we are aware, there is just one literature example of an *aqueous* formulation that is directly analogous to the thermal transition described herein: certain ionic *surfactant* vesicles can form a highly viscous dispersion of anisotropic micelles on heating to 60 °C.^[21] Of perhaps more relevance to the present study, oil thickening has been widely reported for low molecular weight gelators.^[22] However, such gelators are usually heated to obtain a homogeneous solution, with gelation then occurring on cooling. Thus our observations suggest that diblock copolymer vesicles can provide a new high-temperature oil-thickening mechanism.

In summary, PSMA₁₃-PBzMA₉₆ vesicles prepared directly in mineral oil via PISA undergo an order-order morphological transition on heating from 20 °C to 150 °C. This system has been characterized using TEM, SAXS, rheology and variable temperature ¹H NMR spectroscopy. The latter technique confirms that greater solvation of the PBzMA core-forming block occurs at elevated temperatures. Such surface plasticization triggers the observed morphological transition above 135 °C, as indicated by SAXS, TEM and rheology studies. This vesicle-to-worm transition provides a unique high-temperature oil-thickening mechanism that may offer some commercial utility.

Experimental Section

See Supporting Information for Experimental Section.

Acknowledgements


SPA acknowledges an ERC *Advanced Investigator* grant (PISA 320372) and an EPSRC Platform grant (EP/J007846/1). We are grateful to the European Synchrotron Radiation Facility for providing synchrotron beam-time and thank Dr. S. Prevost and the personnel of ID02 for their assistance. Dr. G. Akien of The University of Lancaster, UK is thanked for his assistance with the variable temperature ¹H NMR studies.

Keywords: Polymerization-Induced Self-Assembly • Block copolymers • Nanoparticles • Morphology transition • High-temperature oil thickening

- [1] H. Wennerström, B. Lindman, *Physics Reports* **1979**, *52*, 1-86.
- [2] a) A. D. Bangham, R. W. Horne, *Journal of Molecular Biology* **1964**, *8*, 660; b) A. D. Bangham, *Progress in biophysics and molecular biology* **1968**, *18*, 29-95.
- [3] J. N. Israelachvili, D. J. Mitchell, B. W. Ninham, *Journal of the Chemical Society-Faraday Transactions* **1976**, *72*, 1525-1568.
- [4] L. F. Zhang, A. Eisenberg, *Science* **1995**, *268*, 1728-1731.
- [5] Y. Y. Won, H. T. Davis, F. S. Bates, *Science* **1999**, *283*, 960-963.
- [6] M. Antonietti, S. Förster, *Advanced Materials* **2003**, *15*, 1323-1333.
- [7] a) B. Charleux, G. Delaittre, J. Rieger, F. D'Agosto, *Macromolecules* **2012**, *45*, 6753-6765; b) M. J. Monteiro, M. F. Cunningham, *Macromolecules* **2012**, *45*, 4939-4957; c) N. J. Warren, S. P. Armes, *Journal of the American Chemical Society* **2014**, *136*, 10174-10185.
- [8] a) M. Semsarilar, E. R. Jones, A. Blanazs, S. P. Armes, *Advanced Materials* **2012**, *24*, 3378-3382; b) Y. Pei, A. B. Lowe, *Polymer Chemistry* **2014**, *5*, 2342-2351; c) J.-T. Sun, C.-Y. Hong, C.-Y. Pan, *Polymer Chemistry* **2013**, *4*, 873-881.
- [9] a) L. Houillot, C. Bui, M. Save, B. Charleux, C. Farcet, C. Moire, J.-A. Raust, I. Rodriguez, *Macromolecules* **2007**, *40*, 6500-6509; b) L. A. Fielding, M. J. Derry, V. Ladmira, J. Rosselgong, A. M. Rodrigues, L. P. D. Ratcliffe, S. Sugihara, S. P. Armes, *Chemical Science* **2013**, *4*, 2081-2087; c) M. J. Derry, L. A. Fielding, S. P. Armes, *Progress in Polymer Science* **2016**, *52*, 1-18.
- [10] a) M. J. Derry, L. A. Fielding, N. J. Warren, C. J. Mable, A. J. Smith, O. O. Mykhaylyk, S. P. Armes, *Chemical Science* **2016**; b) A. Blanazs, J. Madsen, G. Battaglia, A. J. Ryan, S. P. Armes, *Journal of the American Chemical Society* **2011**, *133*, 16581-16587; c) D. Zehm, L. P. D. Ratcliffe, S. P. Armes, *Macromolecules* **2013**, *46*, 128-139.
- [11] C. Gonzato, M. Semsarilar, E. R. Jones, F. Li, G. J. P. Krooshof, P. Wyman, O. O. Mykhaylyk, R. Tuinier, S. P. Armes, *Journal of the American Chemical Society* **2014**, *136*, 11100-11106.
- [12] N. J. Warren, O. O. Mykhaylyk, A. J. Ryan, M. Williams, T. Doussineau, P. Dugourd, R. Antoine, G. Portale, S. P. Armes, *Journal of the American Chemical Society* **2015**, *137*, 1929-1937.
- [13] A. Blanazs, R. Verber, O. O. Mykhaylyk, A. J. Ryan, J. Z. Heath, C. W. I. Douglas, S. P. Armes, *Journal of the American Chemical Society* **2012**, *134*, 9741-9748.
- [14] a) Y. W. Pei, N. C. Dharsana, J. A. Van Hensbergen, R. P. Burford, P. J. Roth, A. B. Lowe, *Soft Matter* **2014**, *10*, 5787-5796; b) L. A. Fielding, J. A. Lane, M. J. Derry, O. O. Mykhaylyk, S. P. Armes, *Journal of the American Chemical Society* **2014**, *136*, 5790-5798; c) M. J. Derry, L. A. Fielding, S. P. Armes, *Polymer Chemistry* **2015**, *6*, 3054-3062; d) Y. Pei, L. Thuraijah, O. R. Sugita, A. B. Lowe, *Macromolecules* **2015**, *48*, 236-244.
- [15] J. Bang, S. M. Jain, Z. B. Li, T. P. Lodge, J. S. Pedersen, E. Kesselman, Y. Talmon, *Macromolecules* **2006**, *39*, 1199-1208.
- [16] J. S. Pedersen, *Journal of Applied Crystallography* **2000**, *33*, 637-640.
- [17] A. Rank, S. Hauschild, S. Förster, R. Schubert, *Langmuir* **2009**, *25*, 1337-1344.
- [18] N. P. Truong, J. F. Quinn, M. R. Whittaker, T. P. Davis, *Polymer Chemistry* **2016**, *7*, 4295-4312.
- [19] a) H. Vogel, *Physikalische Zeitschrift* **1921**, *22*, 645-646; b) G. Tammann, W. Hesse, *Zeitschrift für anorganische und allgemeine Chemie* **1926**, *156*, 245-257; c) G. S. Fulcher, *J. Am. Ceram. Soc.* **1925**, *8*, 339-355; d) E. Andrade, *Nature* **1930**, *125*, 309-310.
- [20] V. Lenaerts, C. Triqueneaux, M. Quarton, F. Riegelsalson, P. Couvreur, *International Journal of Pharmaceutics* **1987**, *39*, 121-127.
- [21] a) P. A. Hassan, B. S. Valaulikar, C. Manohar, F. Kern, L. Bourdieu, S. J. Candau, *Langmuir* **1996**, *12*, 4350-4357; b) T. S. Davies, A. M. Ketner, S. R. Raghavan, *Journal of the American Chemical Society* **2006**, *128*, 6669-6675.
- [22] a) K. Hanabusa, M. Suzuki, *Polym J* **2014**, *46*, 776-782; b) B. O. Okesola, D. K. Smith, *Chemical Society Reviews* **2016**, *45*, 4226-4251.

Entry for the Table of Contents

COMMUNICATION

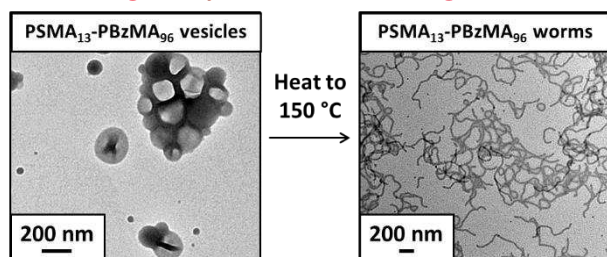A new high-temperature oil-thickening mechanism

Matthew J. Derry,* Oleksandr O. Mykhaylyk and Steven P. Armes*

Page No. – Page No.

**A Vesicle-to-Worm Transition
Provides a New High-Temperature Oil
Thickening Mechanism**

Poly(stearyl methacrylate)₁₃-poly(benzyl methacrylate)₉₆ vesicles in mineral oil undergo a thermally-induced vesicle-to-worm transition, providing a new high-temperature oil-thickening mechanism.